

AD

MEMORANDUM REPORT ARCCB-MR-00007

**A FRACTOGRAPHIC STUDY OF  
A CIRCA AD83 ROMAN NAIL**

**A. A. KAPUSTA  
J. H. UNDERWOOD**

MAY 2000



**US ARMY ARMAMENT RESEARCH,  
DEVELOPMENT AND ENGINEERING CENTER  
CLOSE COMBAT ARMAMENTS CENTER  
BENÉT LABORATORIES  
WATERVLIET, N.Y. 12189-4050**



APPROVED FOR PUBLIC RELEASE; DISTRIBUTION UNLIMITED

20010314 139

### **DISCLAIMER**

The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.

The use of trade name(s) and/or manufacturer(s) does not constitute an official endorsement or approval.

### **DESTRUCTION NOTICE**

For classified documents, follow the procedures in DoD 5200.22-M, Industrial Security Manual, Section II-19, or DoD 5200.1-R, Information Security Program Regulation, Chapter IX.

For unclassified, limited documents, destroy by any method that will prevent disclosure of contents or reconstruction of the document.

For unclassified, unlimited documents, destroy when the report is no longer needed. Do not return it to the originator.

REPORT DOCUMENTATION PAGE			Form Approved OMB No. 0704-0188	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.				
1. AGENCY USE ONLY (Leave blank)	2. REPORT DATE May 2000	3. REPORT TYPE AND DATES COVERED Final		
4. TITLE AND SUBTITLE A FRACTOGRAPHIC STUDY OF A CIRCA AD83 ROMAN NAIL			5. FUNDING NUMBERS PRON No. ALLIANTTECH	
6. AUTHOR(S) A.A. Kapusta (Materials Analytical Services, Duanesburg, NY) and J.H. Underwood				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) U.S. Army ARDEC Benet Laboratories, AMSTA-AR-CCB-O Watervliet, NY 12189-4050			8. PERFORMING ORGANIZATION REPORT NUMBER ARCCB-MR-00007	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) U.S. Army ARDEC Close Combat Armaments Center Picatinny Arsenal, NJ 07806-5000			10. SPONSORING/MONITORING AGENCY REPORT NUMBER	
11. SUPPLEMENTARY NOTES Submitted to <i>Ironmaking and Steelmaking (UK)</i>				
12a. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release; distribution unlimited.			12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) Results are presented of a scanning electron microscope fractographic study of a circa AD83 iron nail from the Roman fortress at Inchtuthil, Perthshire, Scotland. The fracture surface studied was created under embrittling conditions of low temperature, an added stress raiser, and high strain-rate loading. Fractographic features are discussed in relationship to the classic cataloguing and metallographic examination of the Inchtuthil nails in earlier work by Angus, Brown, and Cleere.				
14. SUBJECT TERMS Scanning Electron Fractography, Roman Nail, Iron, Roman Fortress			15. NUMBER OF PAGES 10	
			16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT UNCLASSIFIED	18. SECURITY CLASSIFICATION OF THIS PAGE UNCLASSIFIED	19. SECURITY CLASSIFICATION OF ABSTRACT UNCLASSIFIED	20. LIMITATION OF ABSTRACT UL	

## TABLE OF CONTENTS

	<u>Page</u>
ACKNOWLEDGEMENT.....	ii
INTRODUCTION.....	1
RESULTS.....	1
CONCLUDING REMARKS .....	2
REFERENCES.....	3

## LIST OF ILLUSTRATIONS

1.	A group "D" nail from the Roman fortress at Inchtuhil (1X).....	4
2.	Transverse fracture surface showing notch, corner defect, and fissure (20X) .....	4
3.	Oxide layer on preexisting corner defect (1000X).....	5
4.	Low-temperature transgranular cleavage near crack origin (1000X).....	5
5.	Low-temperature transgranular cleavage remote from crack origin (1000X).....	6
6.	Transverse fracture surface near the laboratory-induced notch (100X) .....	6
7.	Low-temperature transgranular cleavage adjacent to notch (1000X).....	7
8.	Low-temperature transgranular cleavage adjacent to notch (5000X).....	7
9.	Curved 'river lines' indicating cold-worked metal (1000X).....	8
10.	Oxide and voids indicating the preexisting fissure (1000X).....	8

## **ACKNOWLEDGEMENT**

The authors are pleased to acknowledge the help and encouragement of Dr. Anthony P. Parker of Cranfield University, Swindon, England.

## INTRODUCTION

The subject nail was from a store of several hundred thousand discovered in a 4-m deep pit at the Roman legionary fortress at Inchtuthil, Perthshire, Scotland. A sample of these iron nails was catalogued and examined in a paper by Angus *et al.* (ref 1). Microstructure, chemical composition, size and configuration, hardness, and methods of manufacture were described in detail in the previous work. However, the publication of Reference 1 in 1962 predated commercially available scanning electron microscopes. At that time, high-resolution fractography could only be accomplished through the tedious task of replication followed by transmission electron microscopy; accordingly, no fractographic illustrations were presented. This current study uses the scanning electron microscope to document the fracture surface of one nail broken under embrittling conditions: low temperature, an added stress riser, and high strain-rate loading.

## RESULTS

Measuring about 84-mm long with a disk-shaped head, the nail corresponded to one of group "D" as classified in the previous work. Figure 1 shows the as-received nail at 1X magnification, and reveals the roughly rectangular shape of the nail shank and the surprisingly light surface oxide layers discussed in the previous work.

The nail was rinsed in acetone to remove loose surface debris; however, the red-brown surface oxide seen in Figure 1 persisted. After introducing a transverse notch with a 0.5-mm thick cutting wheel, the nail was submerged in a liquid nitrogen bath until boiling had subsided (indicative of stabilization to liquid nitrogen temperature). It was quickly locked into a vise, and easily broken into two pieces with a light hammer blow. The two sections were immediately placed into a room-temperature alcohol bath to preclude fracture surface oxidation by surface condensate. The notch had a depth of about 0.5 mm, and was located about 19 mm from the nail head, where the rectangular shank cross section measured about 5 mm by 5 mm. This resulted in a notch depth of about one-tenth of the shank thickness.

Figure 2 is a view normal to the fracture surface, and it shows that only a small portion of the laboratory-created fracture surface had initiated at the introduced notch, indicated by the letter "N." Most of the fracture had started at a preexisting transverse corner defect, "C." A preexisting longitudinal fissure, "FF," separates the laboratory-created fracture area that initiated at the corner defect and the area that initiated at the introduced notch. The preexisting corner defect and fissure were coated with a black (high-temperature) oxide, and they have a similar appearance to the internal defects seen in a longitudinal metallographic cross section of a group "D" nail shown in Figure 13 of Reference 1. Figures 3 and 4 (from locations shown in Figure 2) are from the oxide covered preexisting corner defect and the "clean" laboratory separation, respectively. The oxide obscures most other features in Figure 3. Figure 4 shows typical low-temperature transgranular cleavage, consistent with cleavage of sound, homogenous steel. Figure 5 is from a region most remote from the crack origin, and again shows transgranular cleavage, and a thin lip of tear dimples, "D."

Figures 6 through 10 are from the laboratory-created fracture surface that initiated at the introduced notch, with the locations of Figures 7 through 10 noted in Figure 6. Figures 7 and 8, at 1000X and 5000X, respectively, show areas of transgranular cleavage immediately adjacent to the notch. Figure 9 shows curved river lines, "R," indicative of transgranular cleavage through preexisting cold worked metal adjacent to the notch, while Figure 10 shows oxide, "O," and small voids, "V," associated with the preexisting longitudinal fissure, "FF."

## **CONCLUDING REMARKS**

This study shows that fracture of this nail under embrittling conditions occurred by typical low-temperature transgranular cleavage, consistent with what would be observed in present-day steel. However, the defects that are present due to poor workmanship during forging, discussed in Reference 1, are seen to have considerable control over the fracture behavior of the nail. These defects could have resulted in the failure of some of these nails by cleavage fracture, especially when improperly driven at low temperature.

## REFERENCES

1. Angus, N.S., Brown, G.T., and Cleere, H.F., "The Iron Nails from the Roman Legionary Fortress at Inchtuthil, Perthshire," *Journal of the Iron and Steel Institute*, November 1962, pp. 956-967.



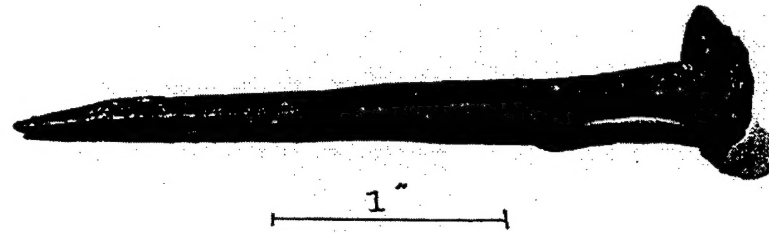


Figure 1. A group "D" nail from the Roman fortress at Inchtuhil (1X).

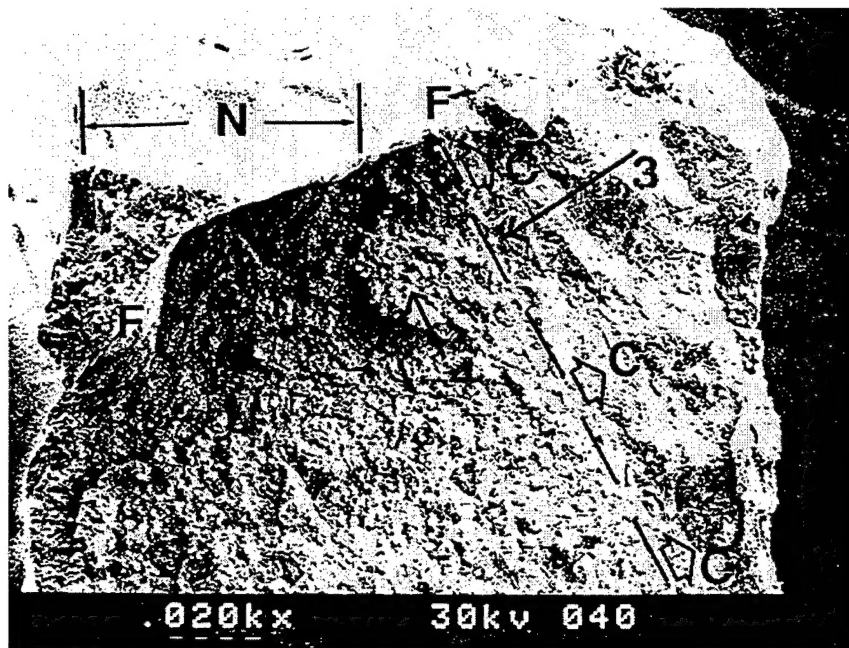


Figure 2. Transverse fracture surface showing notch, corner defect, and fissure (20X).

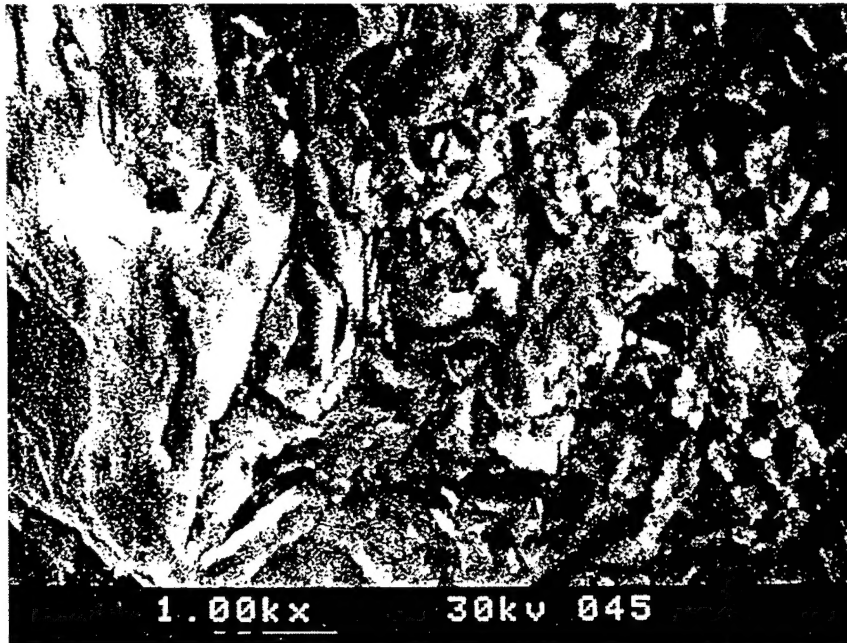


Figure 3. Oxide layer on preexisting corner defect (1000X).

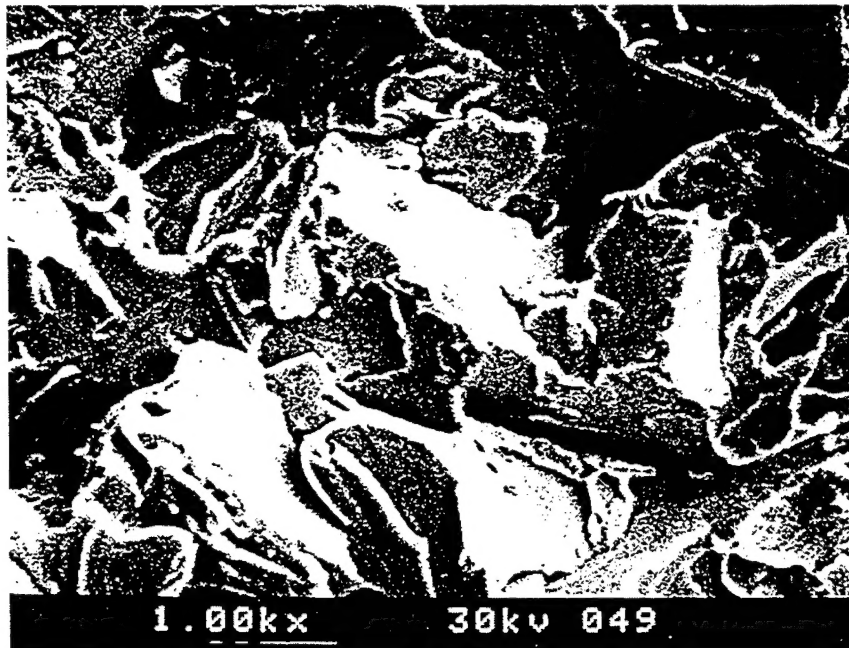


Figure 4. Low-temperature transgranular cleavage near crack origin (1000X).

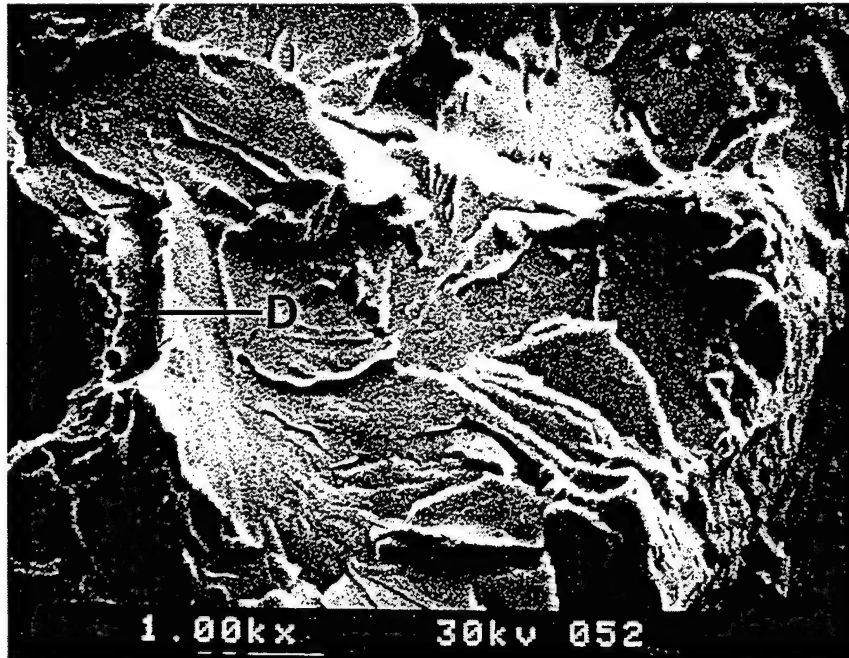


Figure 5. Low-temperature transgranular cleavage remote from crack origin (1000X).

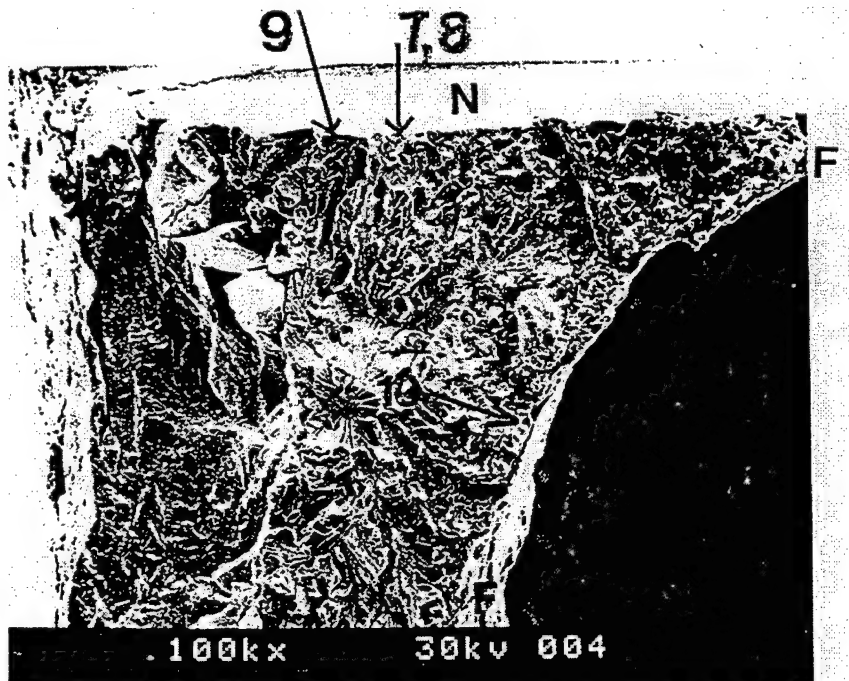


Figure 6. Transverse fracture surface near the laboratory-induced notch (100X).

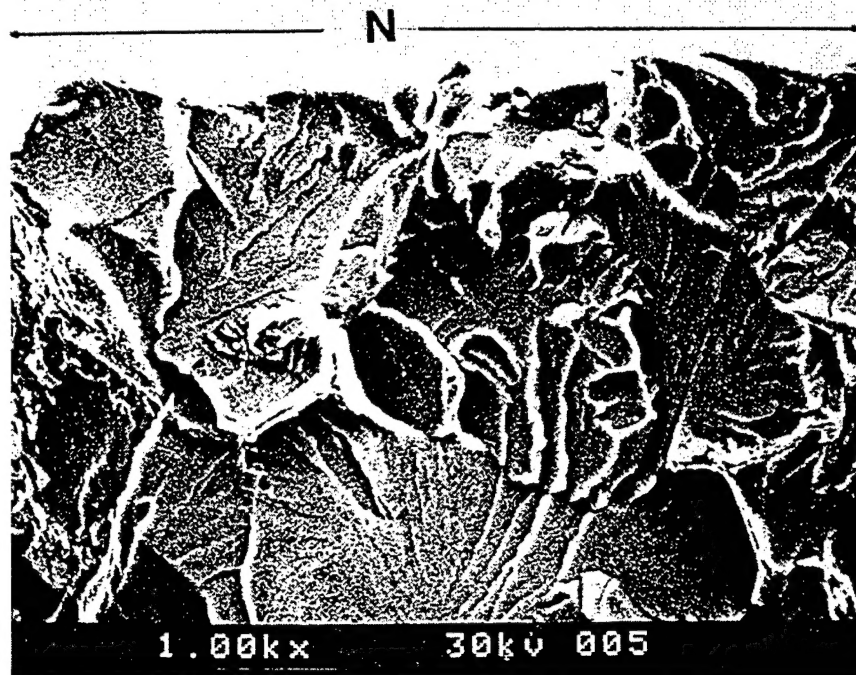


Figure 7. Low-temperature transgranular cleavage adjacent to notch (1000X).

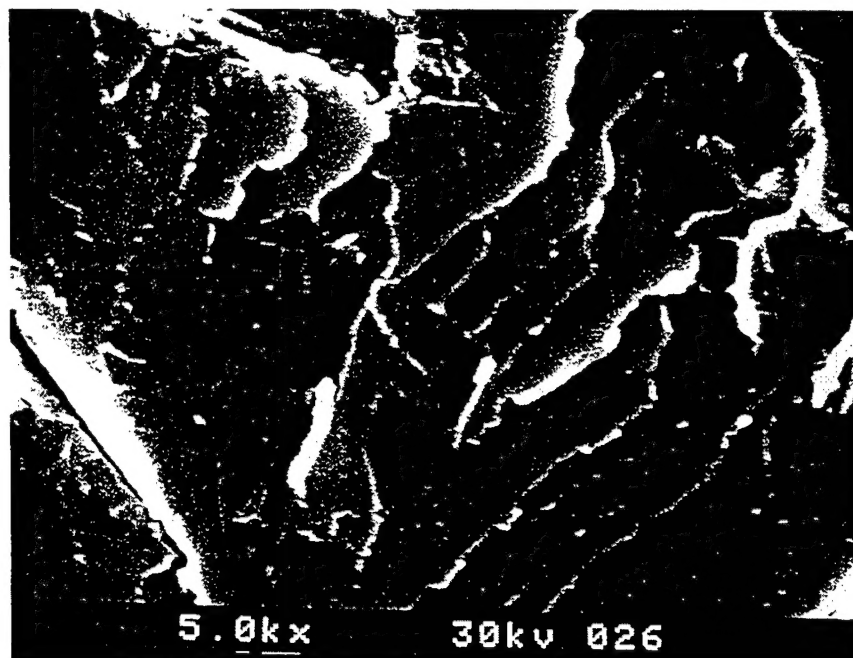


Figure 8. Low-temperature transgranular cleavage adjacent to notch (5000X).



Figure 9. Curved 'river lines' indicating cold-worked metal (1000X).



Figure 10. Oxide and voids indicating the preexisting fissure (1000X).

---

TECHNICAL REPORT INTERNAL DISTRIBUTION LIST

	<u>NO. OF COPIES</u>
TECHNICAL LIBRARY ATTN: AMSTA-AR-CCB-O	5
TECHNICAL PUBLICATIONS & EDITING SECTION ATTN: AMSTA-AR-CCB-O	3
OPERATIONS DIRECTORATE ATTN: SIOWV-ODP-P	1
DIRECTOR, PROCUREMENT & CONTRACTING DIRECTORATE ATTN: SIOWV-PP	1
DIRECTOR, PRODUCT ASSURANCE & TEST DIRECTORATE ATTN: SIOWV-QA	1

NOTE: PLEASE NOTIFY DIRECTOR, BENÉT LABORATORIES, ATTN: AMSTA-AR-CCB-O OF ADDRESS CHANGES.

---

---

TECHNICAL REPORT EXTERNAL DISTRIBUTION LIST

	<u>NO. OF COPIES</u>		<u>NO. OF COPIES</u>
DEFENSE TECHNICAL INFO CENTER		COMMANDER	
ATTN: DTIC-OCA (ACQUISITIONS)	2	ROCK ISLAND ARSENAL	
8725 JOHN J. KINGMAN ROAD		ATTN: SIORI-SEM-L	1
STE 0944		ROCK ISLAND, IL 61299-5001	
FT. BELVOIR, VA 22060-6218			
COMMANDER		COMMANDER	
U.S. ARMY ARDEC		U.S. ARMY TANK-AUTMV R&D COMMAND	
ATTN: AMSTA-AR-WEE, BLDG. 3022	1	ATTN: AMSTA-DDL (TECH LIBRARY)	1
AMSTA-AR-AET-O, BLDG. 183	1	WARREN, MI 48397-5000	
AMSTA-AR-FSA, BLDG. 61	1		
AMSTA-AR-FSX	1	COMMANDER	
AMSTA-AR-FSA-M, BLDG. 61 SO	1	U.S. MILITARY ACADEMY	
AMSTA-AR-WEL-TL, BLDG. 59	2	ATTN: DEPT OF CIVIL & MECH ENGR	1
PICATINNY ARSENAL, NJ 07806-5000		WEST POINT, NY 10966-1792	
DIRECTOR		U.S. ARMY AVIATION AND MISSILE COM	
U.S. ARMY RESEARCH LABORATORY		REDSTONE SCIENTIFIC INFO CENTER	2
ATTN: AMSRL-DD-T, BLDG. 305	1	ATTN: AMSAM-RD-OB-R (DOCUMENTS)	
ABERDEEN PROVING GROUND, MD		REDSTONE ARSENAL, AL 35898-5000	
21005-5066			
		COMMANDER	
DIRECTOR		U.S. ARMY FOREIGN SCI & TECH CENTER	
U.S. ARMY RESEARCH LABORATORY		ATTN: DRXST-SD	1
ATTN: AMSRL-WM-MB (DR. B. BURNS)	1	220 7TH STREET, N.E.	
ABERDEEN PROVING GROUND, MD		CHARLOTTESVILLE, VA 22901	
21005-5066			
COMMANDER			
U.S. ARMY RESEARCH OFFICE			
ATTN: TECHNICAL LIBRARIAN	1		
P.O. BOX 12211			
4300 S. MIAMI BOULEVARD			
RESEARCH TRIANGLE PARK, NC 27709-2211			

---

NOTE: PLEASE NOTIFY COMMANDER, ARMAMENT RESEARCH, DEVELOPMENT, AND ENGINEERING CENTER,  
BENÉT LABORATORIES, CCAC, U.S. ARMY TANK-AUTOMOTIVE AND ARMAMENTS COMMAND,  
AMSTA-AR-CCB-O, WATERVLIET, NY 12189-4050 OF ADDRESS CHANGES.

---